

*27th International Symposium on Analytical and Environmental Problems*



***PROCEEDINGS OF THE***

***27<sup>th</sup> International Symposium***  
***on Analytical and Environmental Problems***

***Szeged, Hungary***  
***November 22-23, 2021***



**University of Szeged**

**Edited by:**  
Tünde Alapi  
Róbert Berkecz  
István Ilisz

**Publisher:**  
University of Szeged, H-6720 Szeged, Dugonics tér 13,  
Hungary

**ISBN 978-963-306-835-9**

**2021.**  
**Szeged, Hungary**

***The 27<sup>th</sup> International Symposium on Analytical and Environmental Problems***

**Organized by:**

SZAB Kémiai Szakbizottság Analitikai és Környezetvédelmi Munkabizottsága

**Supporting Organizations**

*Institute of Pharmaceutical Analysis, University of Szeged  
Department of Inorganic and Analytical Chemistry, University of Szeged*

**Symposium Chairman:**

*István Ilisz, DSc*

**Honorary Chairman:**

*Zoltán Galbács, PhD*

**Organizing Committee:**

*István Ilisz, DSc*

*professor of chemistry*

*University of Szeged, Institute of Pharmaceutical Analysis*

*Tünde Alapi, PhD*

*assistant professor*

*University of Szeged, Department of Inorganic and Analytical Chemistry*

*Róbert Berkecz, PhD*

*assistant professor*

*University of Szeged, Institute of Pharmaceutical Analysis*

**Scientific Committee:**

*István Ilisz, DSc*

*Tünde Alapi, PhD*

*Róbert Berkecz, PhD*

*Daniela Sojic Merkulov, PhD*

*associate professor*

*University of Novi Sad, Faculty of Sciences, Department of Chemistry, Biochemistry and Environmental Protection*

## **Lecture Proceedings**

## ADSORPTION OF Pb<sup>2+</sup> IONS ON GAMMA IRRADIATED PLUM POMACE BIOCHAR

**Durica Katnić, Marija Kojić, Julijana Tadić, Bojana Vasiljević, Milena Marinović-Cincović, Aleksandar Krstić, Slavica Porobić**

*Vinča Institute of Nuclear Sciences - National Institute of the Republic of Serbia, University of Belgrade, P. O. Box 522, 11001 Belgrade, Serbia  
e-mail: djurica.katnic@vin.bg.ac.rs*

### **Abstract**

Removal of heavy metals is important because of their toxic effects on living organisms and unwanted anthropogenic effects. Biochar is suitable as an adsorbent of heavy metals due to its advantages such as various sources of biomass, a large number of microporous channels and surface functional groups, as well as due to its economic viability. There is no data about the plum pomace biochar usage as adsorbent for lead removal. In this study, the plum pomace biochar modified with gamma irradiation (IrPP) is used for the removal of Pb<sup>2+</sup> ions from the aqueous solution. The SEM micrographs revealed that surface morphology of plum pomace is suitable for metal adsorption. The results of adsorption kinetics demonstrated that the removal process of Pb<sup>2+</sup> ions onto IrPP follows a pseudo-second kinetic model, which is confirmed by a better agreement between  $q_{e,cal}=227 \text{ mg g}^{-1}$  and  $q_{e,exp}=224 \text{ mg g}^{-1}$ . Therefore, based on preliminary research, it can be concluded that IrPP originating from biowaste is a promising, eco-friendly sorbent of heavy metal from wastewater.

### **Introduction**

Due to the uncontrolled release of toxic substances from various industrial facilities into the environment, the problem of environmental pollution has arisen. A large number of scientific researches are directed towards the protection and preservation of the environment, and thus of human health.

Biomass as a natural mixture of hydrocarbons is an excellent precursor for obtaining carbon materials. The use of biomass has significant economic and technical advantages. Waste lignocellulosic biomass is used as a raw material for fuel production, heat energy, as well as for adsorption of heavy metals and organic pollutants. In many countries, waste biomass is disposed of in open landfills, which pollutes the environment instead of being used as an energy source or adsorbent [1,2].

In this work, high temperature pyrolysis was used to convert plum pomace into carbon materials.

Plum occupies a leading position in fruit growing, and is mostly grown in the western part of Serbia. About 80% of the total production of plums is processed into brandy. Extensive production of plums, and then processing of plums in order to obtain brandies, increases the amount of waste biomass that is generated as a by-product of processing. Uncontrolled disposal of pomace can pose a great risk to the environment [3].

In this paper, pyrolysis of plum pomace was performed to obtain carbon material that can be used as an adsorbent of heavy metals. Surface modification of obtain carbon material was done by irradiating the material at the source of Co<sup>60</sup> gamma radiation to improve the adsorption capacity. Scanning electron microscopy (SEM) was used to analyse the morphology of plum pomace before and after irradiation.

The irradiated plum pomace biochar was tested as adsorption materials to remove  $Pb^{2+}$  ions. In order to define kinetics and adsorption process equilibrium, corresponding kinetic models were applied.

### Experimental

Plum pomace biochar (PP) is a carbon-rich material derived from the oxygen-limited pyrolysis of plum pomace waste biomass. PP were produced using pyrolysis at 500 °C. Modification of PP was done using gamma irradiation of 50 kGy at the  $Co^{60}$  source. The surface morphology of the PP before and after radiation (IrPP) was observed by SEM method.

### Adsorption experiments

An estimate of the kinetic adsorption parameters of IrPP was executed in a batch of  $Pb^{2+}$  solutions. The IrPP dose of 0.025 g was added to 25 mL aliquot of 250 mg  $L^{-1}$   $Pb^{2+}$  solution. The mixtures were shaken at the different times interval (5, 10, 15, 30, 60, 90, 120, 150 and 180 min). The samples were filtered and the residual number of tested metals in filtrates were detected by Inductively Coupled Plasma-Optical Emission Spectroscopy (ICP-OES 7400). The adsorption capacity of the  $Pb^{2+}$  ions ( $q_e$ ) were calculated based on the equations (1):

$$q_e (mg g^{-1}) = \frac{(C_0 - C_e)V}{m} \quad (1)$$

where  $C_0$  and  $C_e$  - the initial and equilibrium concentration ( $mg L^{-1}$ ),  $V$ - the volume of the metal solution (mL) and  $m$ -the amount of sorbent (mg).

The adsorption kinetics was simulated with pseudo-first-order and pseudo-second-order models, respectively:

$$\ln(q_e - q_t) = \ln q_e - k_1 \cdot t \quad (2)$$

$$\frac{t}{q_t} = \frac{t}{q_e} + \frac{1}{k_2 q_e^2} \quad (3)$$

where  $q_t$  ( $mg g^{-1}$ ) is the amounts of  $Pb^{2+}$  adsorbed at time,  $k_1$  ( $min^{-1}$ ) and  $k_2$  ( $g mg^{-1} min^{-1}$ ) are the rate constants of pseudo-first and pseudo-second model, respectively.

### Results and discussion

The surface morphology of PP and IrPP was examined by SEM analysis. As can be seen in Figure 1, PP shows a smooth surface with a small number of pores and grooves. On the other hand, the presence of pores and the appearance of small cracks on the surface of IrPP are noticed, which is probably a consequence of PP radiation. Petrović et al. [2] concluded that the formation of pores on the surface of biochar can be useful if this material is used as a sorbent of heavy metals from aqueous solutions, because the pores allow easier internal diffusion of metal ions from wastewater.

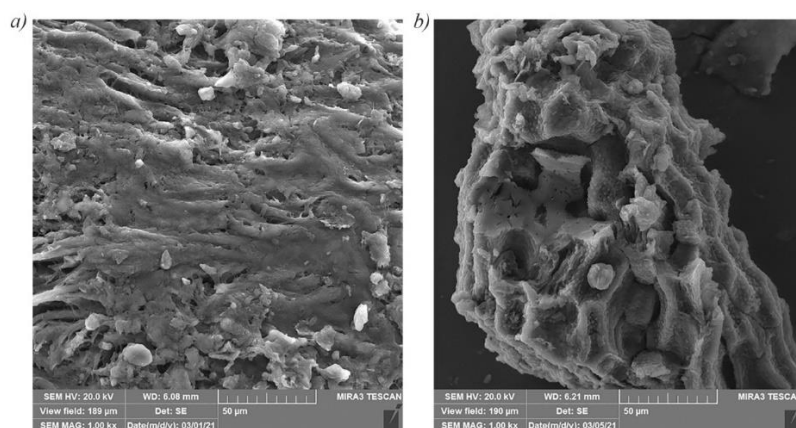


Fig. 1. SEM of PP (a) before and (b) after radiation.

### Adsorption kinetics

The adsorption kinetics of  $Pb^{2+}$  ions by IrPP were presented in Figure 2 and the kinetics parameters were summarized in Table 1.

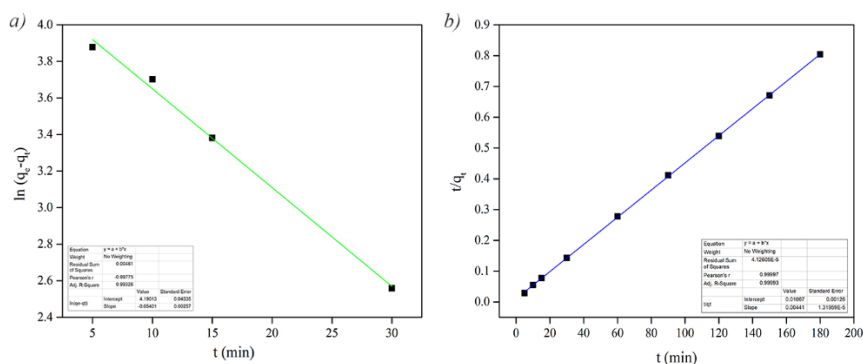


Fig. 2. Pseudo-first-order (a) and pseudo-second-order(a) kinetic adsorption curves of IrPP for  $Pb^{2+}$  ions

Although both models described the kinetic data well with all  $R^2$  higher than 0.99, the pseudo-second-order model gave better fits ( $R^2=0.9999$ ) and compared to pseudo-first-order kinetic model ( $R^2=0.9933$ ), suggesting that the adsorption of  $Pb^{2+}$  by the PP was ascribed to chemical process [4]. Additionally, this was verified with the better agreement of theoretical ( $q_{e,cal}$ ) and experimental results ( $q_{e,exp}$ ) for the pseudo-second model.

Table 1 The kinetic parameters of  $Pb^{2+}$  ions adsorption using IrPP

	Contaminant $Pb^{2+}$
$q_{eq,exp}$ ( $mg\ g^{-1}$ )	224
<b>Pseudo-first-order model</b>	
$q_{eq,cal}$ ( $mg\ g^{-1}$ )	66
$k_1$ ( $min^{-1}$ )	0.124385
$R^2$	0.9933
<b>Pseudo-second-order model</b>	
$q_{eq,cal}$ ( $mg\ g^{-1}$ )	227
$k_2$ ( $g\ mg^{-1}\ min^{-1}$ )	$8.58 \cdot 10^{-08}$
$R^2$	0.9999

### **Conclusion**

Based on preliminary research, the SEM analysis demonstrated that radiation significantly changed the structure of the PP. That is, a large number of pores were observed on the surface of PP after radiation, which facilitate the internal diffusion of  $Pb^{2+}$  from aqueous solutions. Also, on the basis of kinetic analysis, it was confirmed that  $Pb^{2+}$  adsorption is well described by a pseudo-second order kinetic model. These results show that IrPP can be used as a cost-effective sorbent of heavy metals from wastewater.

### **Acknowledgements**

The research was funded by the Ministry of Education, Science and Technological Development of the Republic of Serbia (contract number 451-03-9/2021-14/200017 and 451-03-9/2021-14/200135)

### **References**

- [1] C.G. Khoo, M.K. Lam, A.R. Mohamed, K.T. Lee, *Environ. Res.* 188 (2020) 109828.
- [2] J.T. Petrović, M.D. Stojanović, J.V. Milojković, M.S. Petrović, T.D. Soštarić, M.D. Laušević, M.L. Mihajlović, *J. Environ. Manage.* 182 (2016) 292-300.
- [3] Y. Li, H. Yu, L. Liu, H. Yu, *J. Hazard. Mater.* 420 (2021) 126655.
- [4] M. Petrović, Tatjana Šoštarić, Mirjana Stojanović, Jelena Milojković, Marija Mihajlović, Marija Stanojević, Slavka Stanković, *J. Taiwan Inst. Chem. Eng.* (2015) 1-10.