

Durham Research Online

Deposited in DRO:

24 June 2022

Version of attached file:

Accepted Version

Peer-review status of attached file:

Peer-reviewed

Citation for published item:

Mullins, Abbi Louise and Ćirić, Aleksandar and Zekovic, Ivana and Williams, J. A. Gareth and Dramicanin, Miroslav and Evans, Ivana Radosavljevic (2022) 'Dual-emission luminescence thermometry using LaGaO₃:Cr³⁺, Nd³⁺ phosphors.', *Journal of materials chemistry C* .

Further information on publisher's website:

<https://doi.org/10.1039/D2TC02011D>

Publisher's copyright statement:

This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.

Use policy

The full-text may be used and/or reproduced, and given to third parties in any format or medium, without prior permission or charge, for personal research or study, educational, or not-for-profit purposes provided that:

- a full bibliographic reference is made to the original source
- a [link](#) is made to the metadata record in DRO
- the full-text is not changed in any way

The full-text must not be sold in any format or medium without the formal permission of the copyright holders.


Please consult the [full DRO policy](#) for further details.

Journal of Materials Chemistry C

Materials for optical, magnetic and electronic devices

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: A. L. Mullins, A. Iri, I. Zekovic, G. Williams, M. Dramicanin and I. R. Evans, *J. Mater. Chem. C*, 2022, DOI: 10.1039/D2TC02011D.

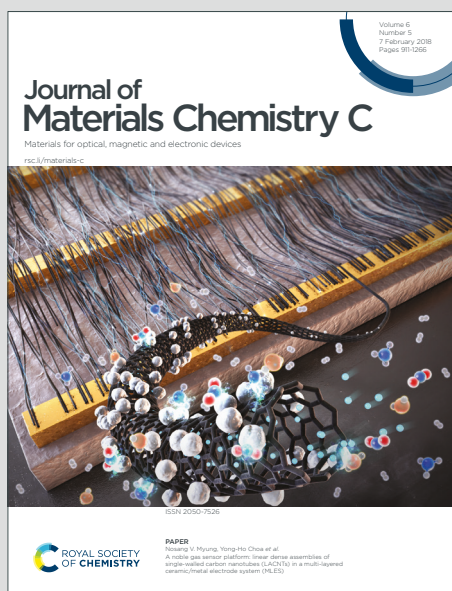

This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Received 00th
January 20xx,Accepted 00th
January 20xxDOI:
10.1039/x0xx00000x**Dual-emission luminescence thermometry using LaGaO₃:Cr³⁺, Nd³⁺ phosphors**Abbi L. Mullins^a, Aleksandar Ćirić^b, Ivana Zeković^b, J. A. Gareth Williams^a, Miroslav D. Dramićanin^{b*} and Ivana Radosavljević Evans^{a*}

A series of La_{1-x}Ga_{0.99}O₃:Cr_{0.01}, Nd_x phosphors (where $x = 0.005, 0.01, 0.02$) for luminescence thermometry was synthesised by the solid-state method, structurally characterised using powder X-ray diffraction data, and investigated by ambient and variable-temperature optical measurements. The design principle relies on the use of a combination of transition metal and rare earth activator ions such that the excitation and emission wavelengths fall within the near infra-red spectral region, notably in the 'first biological window' that is attractive for potential *in vivo* applications. The photoluminescence spectra of the compounds feature the characteristic ²E phosphorescence of Cr³⁺ at 729 nm and the ⁴F_{3/2} → ⁴I_{9/2} emission of Nd³⁺ around 890 nm. The Nd³⁺ emission is quenched at a higher rate than that of Cr³⁺ with increasing temperature. Thermometric analysis by monitoring the luminescence intensity ratio (LIR) between the emissions of Cr³⁺ and Nd³⁺ from 300 K to 650 K shows a quasi-Boltzmann trend, with a maximum relative sensitivity of ~2% K⁻¹, high absolute sensitivity values over this entire temperature range, excellent temperature resolution of 0.04 K at room temperature, and high stability.

1. Introduction

The development of novel ways to accurately monitor small temperature changes is important in numerous applications, including in biomedical systems. Luminescence thermometry is a non-contact method for monitoring temperature changes through their effect on the light-emitting properties of a material, for example, on the intensity of the emission, its decay time, or the profile of the spectrum.¹⁻³ The use of a luminescence intensity ratio (LIR) method is particularly attractive. Here, the ratio of emission at two distinct wavelengths is monitored, rendering the system self-referencing and less dependent on fluctuations in the efficiency of delivery and collection of light.⁴ This approach can allow temperature measurements to be recorded with high accuracy and sensitivity. Most commonly, LIR is observed in systems that can emit from two thermally coupled excited states, according to the following equation:^{5,6}

$$LIR(T) = \frac{I_H(T)}{I_L(T)} = B \cdot \exp(-\Delta E/k_B T) \quad (1)$$

where I_H and I_L are the intensities of the higher- and lower-energy excited states, B is a pre-exponential factor, ΔE is the

energy difference between the thermally coupled states, $k_B = 0.695 \text{ cm}^{-1} \text{ K}^{-1}$ is the Boltzmann constant, and T is the temperature in K. The phosphorescence of one or more activator metal ions doped into a suitable host material offers a potential for luminescence thermometry using such a strategy. Selection of the host material for a solid-state phosphor is critical in providing both stability and control over many of the luminescence properties of the activators.⁷ Perovskite-type lanthanum gallate (LaGaO₃) has been studied for potential applications in fuel cells, solar cells, and light-emitting displays, amongst others.⁸⁻¹⁰ Several LaGaO₃-based materials have been reported as hosts for LIR luminescence thermometers that exploit either single or dual emissions from activator ions. For example, LaGaO₃:Cr³⁺ was shown by Mondal *et al.* to have a relative sensitivity of 2.07% K⁻¹ at 150 K.¹¹ Back *et al.* demonstrated that LaGaO₃:Nd³⁺ – which has a distinct temperature marker at 417 K corresponding to the structural phase transition from orthorhombic to rhombohedral – showed a relative sensitivity of 1.59% K⁻¹ at 300 K.¹² Meanwhile, materials of composition LaGaO₃:Vⁿ⁺, Nd³⁺ were reported by Kniec *et al.* to offer relative sensitivities of 1.0% K⁻¹ at 268 and 363 K, 0.49% K⁻¹ at 253 K, and 1.44% K⁻¹ at 348 K for the V⁵⁺, V⁴⁺, and V³⁺ doped samples respectively.¹³ Most recently, Li *et al.* reported Sm³⁺, Mn⁴⁺-doped LGO phosphors with a maximum relative sensitivity of 2.09% K⁻¹ at 456 K.¹⁴ Our own recent work has shown that deconvolution of the overlapped temperature-invariant sharp ²E emission from the temperature-dependent broadband ⁴T₂ emission of Cr³⁺ in LaGaO₃ gives a relative sensitivity of ~2.50% K⁻¹ at 300 K and as good temperature resolution as 0.05 K.¹⁵

a. Department of Chemistry, Durham University, Durham DH1 3LE, UK.

E-mail: ivana.radosavljevic@durham.ac.uk

b. Centre of Excellence for Photoconversion, Vinča Institute of Nuclear Sciences – National Institute of the Republic of Serbia, University of Belgrade, P.O. Box 522, Belgrade 11001, Serbia. E-mail: dramican@gmail.com



Lanthanide ions (Ln^{3+}) are in some respects well-suited to luminescence thermometry, owing to their narrow-band emission.^{16–21} However, the requirement for thermally coupled excited states restricts the choice of Ln^{3+} dopant.⁴ Moreover, Ln^{3+} ions suffer from low absorption coefficients such that the population of their excited states by light absorption is inefficient. Transition metal ions typically have broader absorptions and, usually, higher extinction coefficients, reflecting the greater extent to which the Laporte selection rule is relaxed for $d-d$ as opposed to $f-f$ transitions. LIR thermometers based on Cr^{3+} , Mn^{4+} , and Ni^{2+} have been investigated, both as single and dual-doped systems.^{11,22,23,24,25} The Boltzmann equilibrium between the closely separated ^2E and $^4\text{T}_2$ excited states of d^3 ions such as Cr^{3+} underpins them.^{26–29}

The aim of the present study was to combine the complementary advantages of lanthanide and transition metal ions in the design of a luminescent thermometer that would function in the near-infrared (NIR) region. The neodymium(III) ion was selected for investigation with Cr^{3+} , as Nd^{3+} not only emits in the NIR but also has a number of excited states of energies that overlap with the emission of Cr^{3+} , allowing for Cr^{3+} -to- Nd^{3+} energy transfer.¹⁰ The narrow-band nature of the ^2E emission of Cr^{3+} , as well as that of the lanthanide ion, and their separation of >200 nm ensures good discrimination for luminescence thermometry readout. The characteristic Nd^{3+} line emissions fall into the part of the NIR region known as the ‘first biological window’ (biological tissue being relatively transparent to this part of the spectrum), allowing for potential applications in biomedical imaging, including *in vivo* temperature sensing.³⁰ Marciniak *et al.* have reported phosphors utilising the Cr^{3+} , Nd^{3+} combination; for example, the material $\text{LiLaP}_4\text{O}_{12}:\text{Cr}^{3+}_{0.01}$, $\text{Nd}^{3+}_{0.10}$ shows thermometric properties in the physiological temperature range with a relative sensitivity of $4.89\% \text{ K}^{-1}$ at 323K.^{31,32} Here, we report the solid-state synthesis, structural characterisation, and photoluminescence (PL) properties of a series of Cr^{3+} and Nd^{3+} -doped LGO phosphors. Variable-temperature photoluminescence measurements were performed to investigate the excitation, emission, and energy transfer of the system. Extensive thermometric analysis – including sensitivities, temperature resolution and repeatability – was undertaken to characterise the luminescent thermometry performance.

2. Experimental Methods

2.1 Synthesis

All samples were synthesised by conventional solid-state reaction methods from stoichiometric quantities of reactants to prepare 2 g of product.¹² La_2O_3 powder (Aldrich, $\geq 99.99\%$) was pre-heated to 900°C for 10 h to remove moisture. The pre-dried La_2O_3 , Ga_2O_3 (Aldrich, $\geq 99.99\%$), Cr_2O_3 (Aldrich, 99.9%), and Nd_2O_3 (Aldrich, 99.9%) powders were ground for approximately 30 min with an agate mortar and pestle, pressed into 10 mm

pellets, and placed into alumina crucibles with lids. Samples were sintered in a muffle furnace at 1200°C in air for 60–100 h with intermittent grinding.

2.2 Powder X-ray Diffraction (PXRD)

PXRD was used to monitor the progress of the reactions and to determine the purity of the products. All measurements were carried out at room temperature using a Bruker AXS d8 Advance diffractometer utilising $\text{CuK}\alpha$ radiation and a Lynx-Eye detector. Patterns were recorded in a range of $10^\circ < 2\theta < 90^\circ$ with a step size of 0.02° and step time of 0.5 s. All patterns were analysed by Rietveld fitting in TOPAS academic software.^{33,34} Refined parameters included background polynomial terms, zero-point, pseudo-Voigt peak shape function terms, unit cell parameters, and an overall isotropic atomic displacement parameter.

2.3 Photoluminescence Spectroscopy

The PL properties of $\text{La}_{1-x}\text{Ga}_{0.99}\text{O}_3:\text{Cr}_{0.01}, \text{Nd}_x$ ($x = 0.005, 0.01, 0.02$) were studied using a Horiba Jobin-Yvon Fluorolog-3 spectrometer. The excitation source was a 450W xenon lamp. The emitted light was detected using either a red-sensitive photomultiplier tube (Hamamatsu R928) or a CCD detector (Horiba Synapse back-illuminated deep depletion) offering good sensitivity up to 1000 nm. NIR emission at $\lambda > 1000$ nm was monitored using a Hamamatsu NIR photomultiplier tube. Samples were analysed either in 3 mm o.d. quartz capillary tubes within the instrument’s sample compartment, or externally using a Quanta-phi integrating sphere coupled to the instrument with optical fibres. Long-pass 400 nm and 850 nm filters were utilised to remove harmonic peaks in RT excitation and emission spectra. Lifetime data were acquired using an Edinburgh Instruments OB920 following excitation of the samples in 3 mm o.d. quartz capillaries with a microsecond-pulsed flashlamp. Emitted light was detected at right angles using an R928 detector operating in multichannel scaling mode. The variation in PL intensity with temperature over the range 300–650 K was investigated for all Cr^{3+} , Nd^{3+} doped compounds using an Ocean Insight FX spectrometer with bifurcated fibre-optics and a custom-built thermometry apparatus.³⁵ Samples were excited at 473 nm using a 150 mW high-stability laser.

3. Results and Discussion

3.1 Structural characterisation

All PXRD patterns were fitted using orthorhombic LaGaO_3 as the initial structural model.³⁶ Fig. 1 shows the final Rietveld fits obtained and Table 1 summarises main crystallographic parameters.



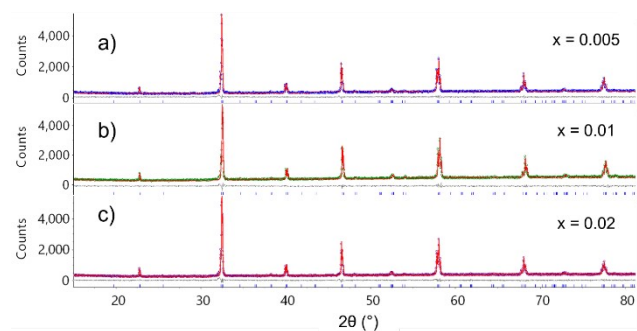


Figure 1: Rietveld fits of the XRD data collected on $\text{La}_{1-x}\text{Ga}_{0.99}\text{O}_3:\text{Cr}_{0.01}, \text{Nd}_x$ – a) $x = 0.005$, b) $x = 0.01$, and c) $x = 0.02$ samples. In each case the red curve represents the calculated pattern; the green, purple, and blue represents the observed data, whilst the difference curve is depicted in grey.

Fig. 2 shows the perovskite-type structure of LaGaO_3 , made up of a network of corner-sharing GaO_6 octahedra with interspersed La^{3+} ions. Having a Goldschmidt tolerance factor $t = 0.973$, LaGaO_3 is orthorhombic, crystallising in space group $Pnma$ (no. 62). The departure from the cubic symmetry is due to the tilting of the GaO_6 octahedra – in Glazer notation, from $a^0a^0a^0$ to $a^+b^-b^-/a^+a^-a^-$ – resulting in the change of the La^{3+} environment and a lowering of the La^{3+} coordination number (CN) from 12 to 8.³⁷ In space group $Pnma$, La^{3+} and Ga^{3+} are located on Wyckoff sites 4c and 4a, with site symmetry m and 1 , respectively. Given the ionic radii of the species involved, it can be expected that Nd^{3+} (1.109 Å, CN = 8) will readily substitute for La^{3+} (1.160 Å, CN = 8), and that Cr^{3+} (0.615 Å, CN = 6) will substitute for Ga^{3+} (0.620 Å, CN = 6).³⁸

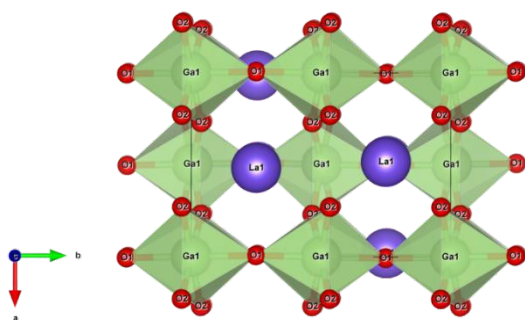


Figure 2: Unit cell of $\text{LaGaO}_3:\text{Cr}_{0.01}, \text{Nd}_{0.02}$ viewed down the crystallographic c -axis. La^{3+} is shown in purple, Ga^{3+} in green, and O^{2-} in red.

Table 1: Refined unit cell parameters for the $\text{La}_{1-x}\text{Ga}_{0.99}\text{O}_3:\text{Cr}_{0.01}, \text{Nd}_x$ ($x = 0.005, 0.01, 0.02$) series.


Sample	R_{wp} (%)	a (Å)	b (Å)	c (Å)	Cell Volume (Å ³)
$\text{La}_{0.995}\text{Nd}_{0.005}\text{Ga}_{0.99}\text{Cr}_{0.01}\text{O}_3$	5.52	5.4924(1)	7.7747(1)	5.5241(1)	235.895(8)
$\text{La}_{0.99}\text{Nd}_{0.01}\text{Ga}_{0.99}\text{Cr}_{0.01}\text{O}_3$	5.35	5.49259(9)	7.7745(1)	5.52399(9)	235.890(7)
$\text{La}_{0.98}\text{Nd}_{0.02}\text{Ga}_{0.99}\text{Cr}_{0.01}\text{O}_3$	5.75	5.4923(1)	7.7745(1)	5.5227(1)	235.828(8)

3.2 Room temperature photoluminescence analysis

Article Online
DOI: 10.1039/D2TC02011D

The emission spectra of all three samples upon the excitation at 590 nm (*i.e.*, in the region of the spin-allowed ${}^4\text{A}_{2g} \rightarrow {}^4\text{T}_{2g}$ absorption of Cr^{3+}) show two well-defined sets of bands: one set in the 700–750 nm region attributable to the ${}^2\text{E}$ emission of Cr^{3+} and the other in the 860–930 nm range due to the ${}^4\text{F}_{3/2} \rightarrow {}^4\text{I}_{9/2}$ transitions of the Nd^{3+} ion (Fig. 3c). The absence of broadband fluorescence corresponding to the strongly field-dependent, spin-allowed ${}^4\text{T}_{2g}$ to ${}^4\text{A}_{2g}$ transition of Cr^{3+} indicates that the Cr^{3+} ions in the CrO_6 octahedra experience a strong-field local environment, such that the ${}^4\text{T}_{2g}$ state lies at significantly higher energy than the ${}^2\text{E}$. The peak at 739 nm for all three samples is indicative of an exchange-coupled $\text{Cr}^{3+}\text{-Cr}^{3+}$ pair N-line.^{39,40} The contribution of the N-line to the spectrum should be concentration-dependent but, as all three samples contain 1.0% Cr^{3+} , the N-line peaks are of approximately equal relative intensity in this instance. Stokes and anti-Stokes sidebands are seen for each sample on either side of the ${}^2\text{E}$ R-line emission.⁴¹

The distinct line-like emission of the Nd^{3+} ${}^4\text{F}_{3/2} \rightarrow {}^4\text{I}_{9/2}$ transition centred at about 890 nm increases with increasing Nd^{3+} concentration relative to the Cr^{3+} ${}^2\text{E}$ emission (Fig. 3c). As the Nd^{3+} concentration increases, there is also evidence of an increasing contribution from the ${}^4\text{F}_{5/2} \rightarrow {}^4\text{I}_{9/2}$ transition at around 800 nm (Fig. 3c). The ${}^4\text{F}_{5/2}$ excited state is thermally coupled to the ${}^4\text{F}_{3/2}$ at room temperature due to the small difference in energy between them.⁴² Fig. 3d gives the NIR emission spectrum of the samples, showing the ${}^4\text{F}_{3/2}$ to ${}^4\text{I}_{11/2}$



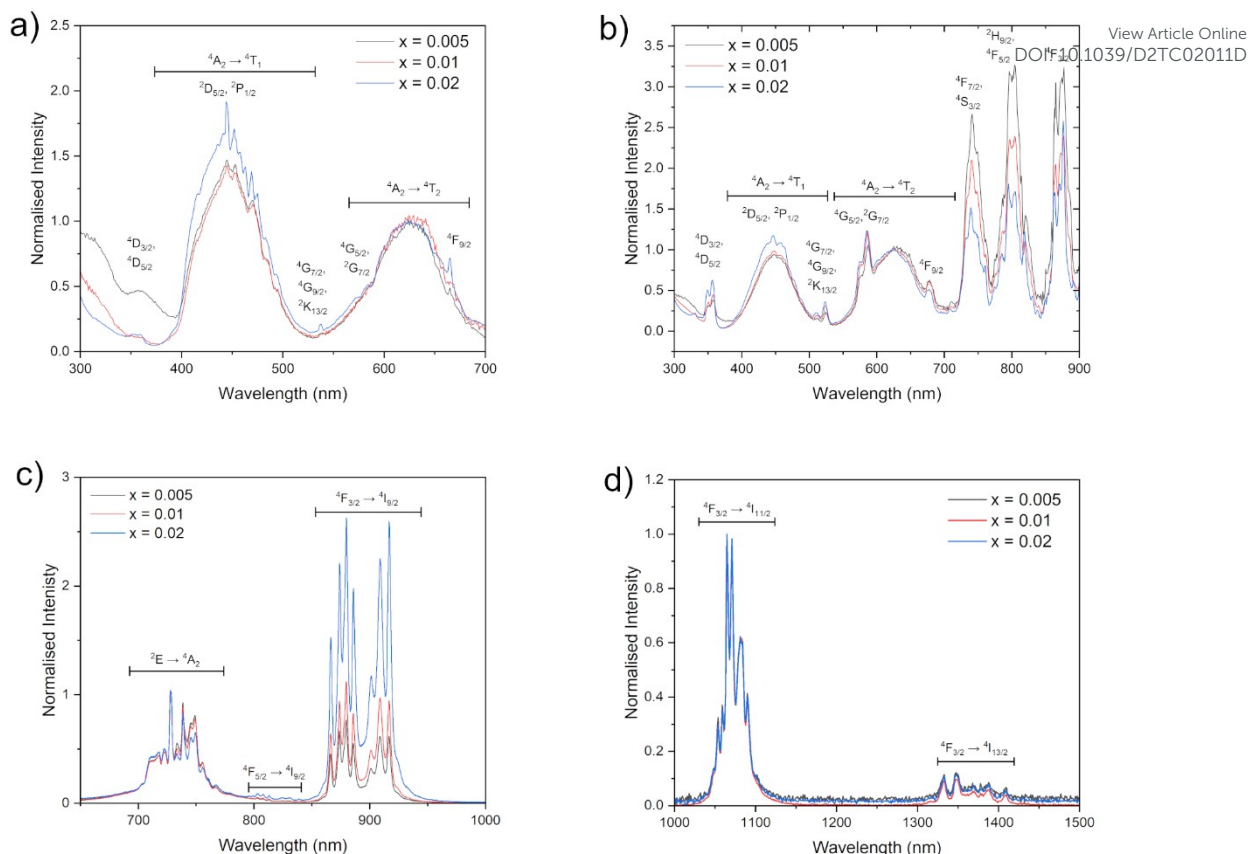


Figure 3: Normalised spectra of La_{1-x}GaO₃:Cr_{0.01}, Nd_x. a) Excitation spectra of Cr³⁺ monitored at $\lambda_{em} = 729$ nm, normalised at 622 nm; b) Excitation spectra of Nd³⁺ monitored at $\lambda_{em} = 1071$ nm, normalised at 622 nm; c) Normalised emission spectra of the three members of the LaGaO₃: Cr, Nd series normalised at 729 nm, $\lambda_{ex} = 590$ nm; d) Emission spectra in the NIR region > 1000 nm, $\lambda_{ex} = 590$ nm.

emission centred at 1070 nm, and ${}^4F_{3/2} \rightarrow {}^4I_{11/2}$ emission centred at 1360 nm. The observed Nd³⁺ emissions could arise, at least in part, from direct excitation of the ${}^4I_{9/2} \rightarrow {}^4G_{5/2}$ transition at the excitation wavelength used, although the ${}^4F_{5/2}$ state could also be populated indirectly by energy transfer from Cr³⁺, given the overlap of the Cr³⁺ 2E emission with excitations of Nd³⁺ to the ${}^4F_{7/2}$, ${}^4S_{3/2}$, and ${}^4F_{9/2}$ states.

Excitation spectra can help to determine whether or not such energy transfer is significant. The excitation spectra of the samples monitored for the Cr³⁺ 2E emission at 729 nm and for the ${}^4F_{3/2} \rightarrow {}^4I_{9/2}$ of Nd³⁺ at 905 nm are shown in Figs. 3a and 3b, respectively. The Cr³⁺ excitation spectrum shows two broad bands at 624 and 444 nm attributed to the Cr³⁺ ${}^4A_{2g} \rightarrow {}^4T_{2g}$ and ${}^4A_{2g} \rightarrow {}^4T_{1g}$ transitions, respectively. There is also some evidence of sharper line-like excitations at 665, 584, 537, 444, and 354 nm, superimposed on the broad Cr³⁺ bands, most evident for the $x = 0.02$ sample with the highest Nd³⁺ concentration. The wavelengths of these peaks correspond well to the energies of the ${}^4F_{9/2}$; ${}^4G_{5/2}$ and ${}^2G_{7/2}$; ${}^4G_{7/2}$, ${}^4G_{9/2}$ and ${}^2K_{13/2}$; ${}^2D_{5/2}$ and ${}^2P_{1/2}$; and ${}^4D_{3/2}$ and ${}^4D_{5/2}$ excited states of Nd³⁺. Their appearance in the excitation spectrum of the Cr³⁺ ions suggests that some Nd³⁺ \rightarrow Cr³⁺ energy transfer is occurring. The Nd³⁺ excitation spectrum, Fig. 3b, shows sharp peaks for excitation to the ${}^4F_{3/2}$ at 880 nm; ${}^2H_{9/2}$ and ${}^4F_{5/2}$ at 810 nm; ${}^4F_{7/2}$ and ${}^4S_{3/2}$ at 740 nm; ${}^4F_{9/2}$ at 680 nm; ${}^4G_{5/2}$ and ${}^2G_{7/2}$ at 590 nm; ${}^4G_{7/2}$, ${}^2G_{9/2}$, and ${}^2K_{13/2}$ at 520 nm; ${}^2D_{5/2}$, and ${}^2P_{1/2}$ at 440 nm; and

${}^4D_{3/2}$, and ${}^4D_{5/2}$ states at 350 nm.⁴² Notably, the excitation spectrum of the Nd³⁺ emission does also prominently feature the broad bands associated with Cr³⁺, suggesting that some Cr³⁺ \rightarrow Nd³⁺ energy transfer is occurring for these materials at room temperature. Energy transfer between activator ions is illustrated schematically in Fig. 4 showing the relative energies of pertinent states on Cr³⁺ and Nd³⁺. The decline in the relative intensity of the Nd³⁺ relative to the Cr³⁺ excitations with

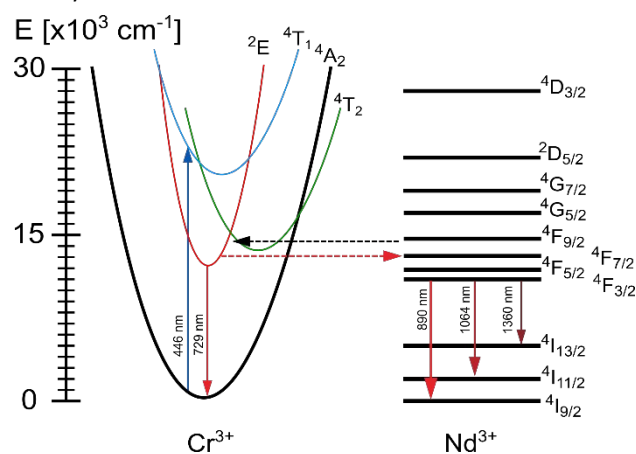


Figure 4: Energy level diagram showing energy transfer between Cr³⁺ and Nd³⁺ ions, with filled straight lines showing emission/excitation, and dashed lines denoting energy transfer from Cr³⁺ to Nd³⁺ in red, and Nd³⁺ to Cr³⁺ in black, respectively.



increasing Nd³⁺ content may be indicative of a degree of quenching between Nd³⁺ ions.

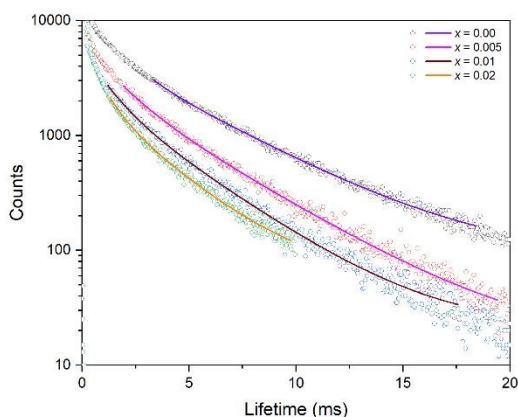


Figure 5: Lifetime data (circles) and bi-exponential fits (lines) of LaGa_{0.99}O₃:Cr_{0.01} ($x = 0.00$) and of La_{1-x}Ga_{0.99}O₃:Cr_{0.01}, Nd_x ($x = 0.005, 0.01, \text{ and } 0.02$).

The lifetimes of the Cr³⁺ emission at 729 nm were measured for LaGa_{0.99}O₃:Cr_{0.01} and the Nd³⁺-doped samples at room temperature, Fig. 5. The data fitted well to a bi-exponential decay with a y offset for dark-count, giving an average lifetime of 4.2 ms for the -Cr³⁺-only sample, compared to values of 3.6, 3.0, and 2.5 ms for the $x = 0.005, 0.01$ and 0.02 samples. The trend of decreasing lifetime of the Cr³⁺ ²E state with increasing Nd³⁺ doping supports the conclusion above that Cr³⁺ → Nd³⁺ energy transfer is occurring. The energy transfer efficiency, η_{ET} , was calculated to be 14%, 28%, and 40% respectively using equation (2), where τ_{Cr} is the lifetime of the chromium-only sample and τ_{Cr-Nd} that of the dual-doped sample.⁴³

$$\eta_{ET} = 1 - \frac{\tau_{Cr-Nd}}{\tau_{Cr}} \quad (2)$$

3.3 Luminescence thermometry

Temperature-dependent spectra of La_{1-x}Ga_{0.99}O₃:Cr_{0.01}, Nd_x phosphors (where $x = 0.005, 0.01, 0.02$) are presented in Figs. 6a-c. As sample La_{0.98}Ga_{0.99}O₃:Cr_{0.01}, Nd_{0.02} showed comparable intensities from the Cr³⁺ and Nd³⁺ ions, it was selected for thermometric evaluation. The 808 nm emission band of Nd³⁺ overlaps with the tail of the broad emission from the ⁴T₂ level of Cr³⁺ and was therefore excluded from the analysis. The pure Cr³⁺ and Nd³⁺ emissions are considered at $\lambda < 790$ nm (N-lines, ²E) and $\lambda > 850$ nm, respectively. The Cr³⁺ emission experiences simultaneous increase of emissions from the ⁴T₂ level and decrease of intensity of emissions from ²E level and N-lines with increasing temperature, such that the overall Cr³⁺ emission intensity is quenched more slowly than the ⁴F_{3/2} → ⁴I_{9/2} emission of Nd³⁺. The intensities were fitted to Eq. 1, where $I_H = I(\text{Cr}^{3+})$, and $I_L = I(\text{Nd}^{3+})$, and the resultant LIR is presented in Fig. 6d. The energy gap used in Eq. 1 does not represent the gap between the thermalised levels, but instead the two emission centres –

the Cr³⁺ and Nd³⁺ activator ions. The quasi-Boltzmann relation to which the experimental data are fitted is given by

$$LIR = \frac{I(\text{Cr}^{3+})}{I(\text{Nd}^{3+})} = 63.9(8) \exp\left(\frac{1170(59)}{k_B T}\right) \quad (3)$$

with a high quality of fit of adj. $R^2 = 0.997$. The fitted energy gap is larger than that between the thermalised levels of all the lanthanides but Eu³⁺, meaning that the relative sensitivity will have a relatively high value. The high value of the temperature-invariant parameter B in Eq. 1 is an indication of the high absolute sensitivity of this probe. The absolute and relative sensitivities respectively (Fig. 5e) were obtained by:

$$S_a [K^{-1}] = \left| \frac{\partial LIR}{\partial T} \right| = \frac{\Delta E}{k_B T^2} B \exp\left(-\frac{\Delta E}{k_B T}\right) \quad (4)$$

$$S_r [\% K^{-1}] = \frac{S_a}{LIR} 100\% = \frac{\Delta E}{k_B T^2} 100\% \quad (5)$$

The relative sensitivity, S_r , was calculated as $\sim 2.0\% K^{-1}$ at 300K, which is, as predicted, a value higher than achieved with most of the lanthanides (see Table 2 in Ref. 4).

The sensor stability was tested and confirmed by estimating LIR while cycling between two temperatures in 10 periods (see Fig. 5f). The LIR values at those temperatures remained unchanged after each cycle. The repeatability was estimated according to:⁴⁴

$$R[\%] = \left(1 - \frac{\max(|\text{mean}(LIR) - LIR_i|)}{\text{mean}(LIR)} \right) \cdot 100\% \quad (6)$$

where i denotes the measurement count. For the measurements presented in Fig. 5f, the repeatability is 99.92% and 99.88% at 350 K and 500 K, respectively.

Finally, the relative uncertainties (σ_r) were estimated from 30 consecutive measurements at 300 K and 435 K, with values of 0.07% and 0.09%, respectively (see Fig. 5g,h). Corresponding temperature resolutions of 0.04 K and 0.1 K were estimated using equation (7).

$$\Delta T = \frac{\sigma_r}{S_r} \quad (7)$$

Although our material does not exhibit the same sensitivity as some other Cr³⁺, Nd³⁺ - containing luminescence thermometers in the literature, it provides high precision and therefore excellent temperature resolution. The reason behind the low uncertainties in temperature measurements using this probe is that both emissions utilised for LIR have high intensities. Swieten et al.⁴⁵ recently demonstrated that signal strength is directly proportional to the precision of the temperature measurement. As already mentioned, Cr³⁺ emission in the strong crystal field is comprised of the ⁴T₂ and ²E bands, with opposite trends with change in temperature. These bands overlap, but as the ⁴T₂ band is broader, there is always a spectral region which comprises only of the ⁴T₂ band. The emission of the entire Cr³⁺ emission, comprised of ⁴T₂ and ²E bands, changes more slowly with temperature than each individual band. By taking a narrow spectral range for LIR, containing only ⁴T₂ emission, the larger uncertainty is introduced than by observing



ARTICLE

Journal Name

the entire Cr^{3+} emission as it is obvious that the entire emission is more intense than any of its individual parts. Thus, the higher sensitivity that can be obtained by employing only ${}^4\text{T}_2$ emission in LIR does not necessarily mean that the temperature resolution is improved, as the increased relative sensitivity can be compensated by the increased uncertainty. The analogous demonstration is presented in our previous work where we showed that by deconvolution of ${}^4\text{T}_2$ and ${}^2\text{E}$ bands the relative sensitivity can be significantly increased, but the temperature resolution stays invariant to the numerical method employed for LIR.⁴⁶ In a YAG matrix, a high temperature sensitivity of $3.48\% \text{ K}^{-1}$ was observed, but only a fraction of Cr^{3+} emission was employed for the integration used for the LIR calculation.⁴⁷ In a Cr^{3+} , Nd^{3+} doped $\text{Y}_3\text{Al}_2\text{Ga}_3\text{O}_{12}$ host, a relative sensitivity of $2.2\% \text{ K}^{-1}$ was observed with even narrower integrated areas.⁴⁸ An investigation of $\text{Gd}_3\text{Ga}_5\text{O}_{12}$ gave a relative sensitivity of $1.90\% \text{ K}^{-1}$ by LIR, using only the ratio of the broad-band of Cr^{3+} divided to the Nd^{3+} emission.²⁴ An outstanding relative sensitivity of $4.89\% \text{ K}^{-1}$ was reported for a Cr^{3+} , Nd^{3+} co-doped system in $\text{LiLaP}_4\text{O}_{12}$ host, but using 20 nm-wide integration windows for both Cr^{3+} and Nd^{3+} , and with high emission intensities only at lower temperatures.³² Thus, in Cr^{3+} , Nd^{3+} co-doped systems, the sensitivity of LIR requires a compromise between the precision of the measurement and the sensitivity. A robust comparison of the most important figure of merit in thermometry – the temperature resolution – in different materials would necessitate measuring all the materials under the same experimental conditions. For comparison of the most prominent and highly performing probes for luminescence thermometry by the LIR method with our sensor please see Table 2.

View Article Online
DOI: 10.1039/D2TC02011D

Open Access Article. Published on 23 June 2022. Downloaded on 6/24/2022 3:58:18 PM.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



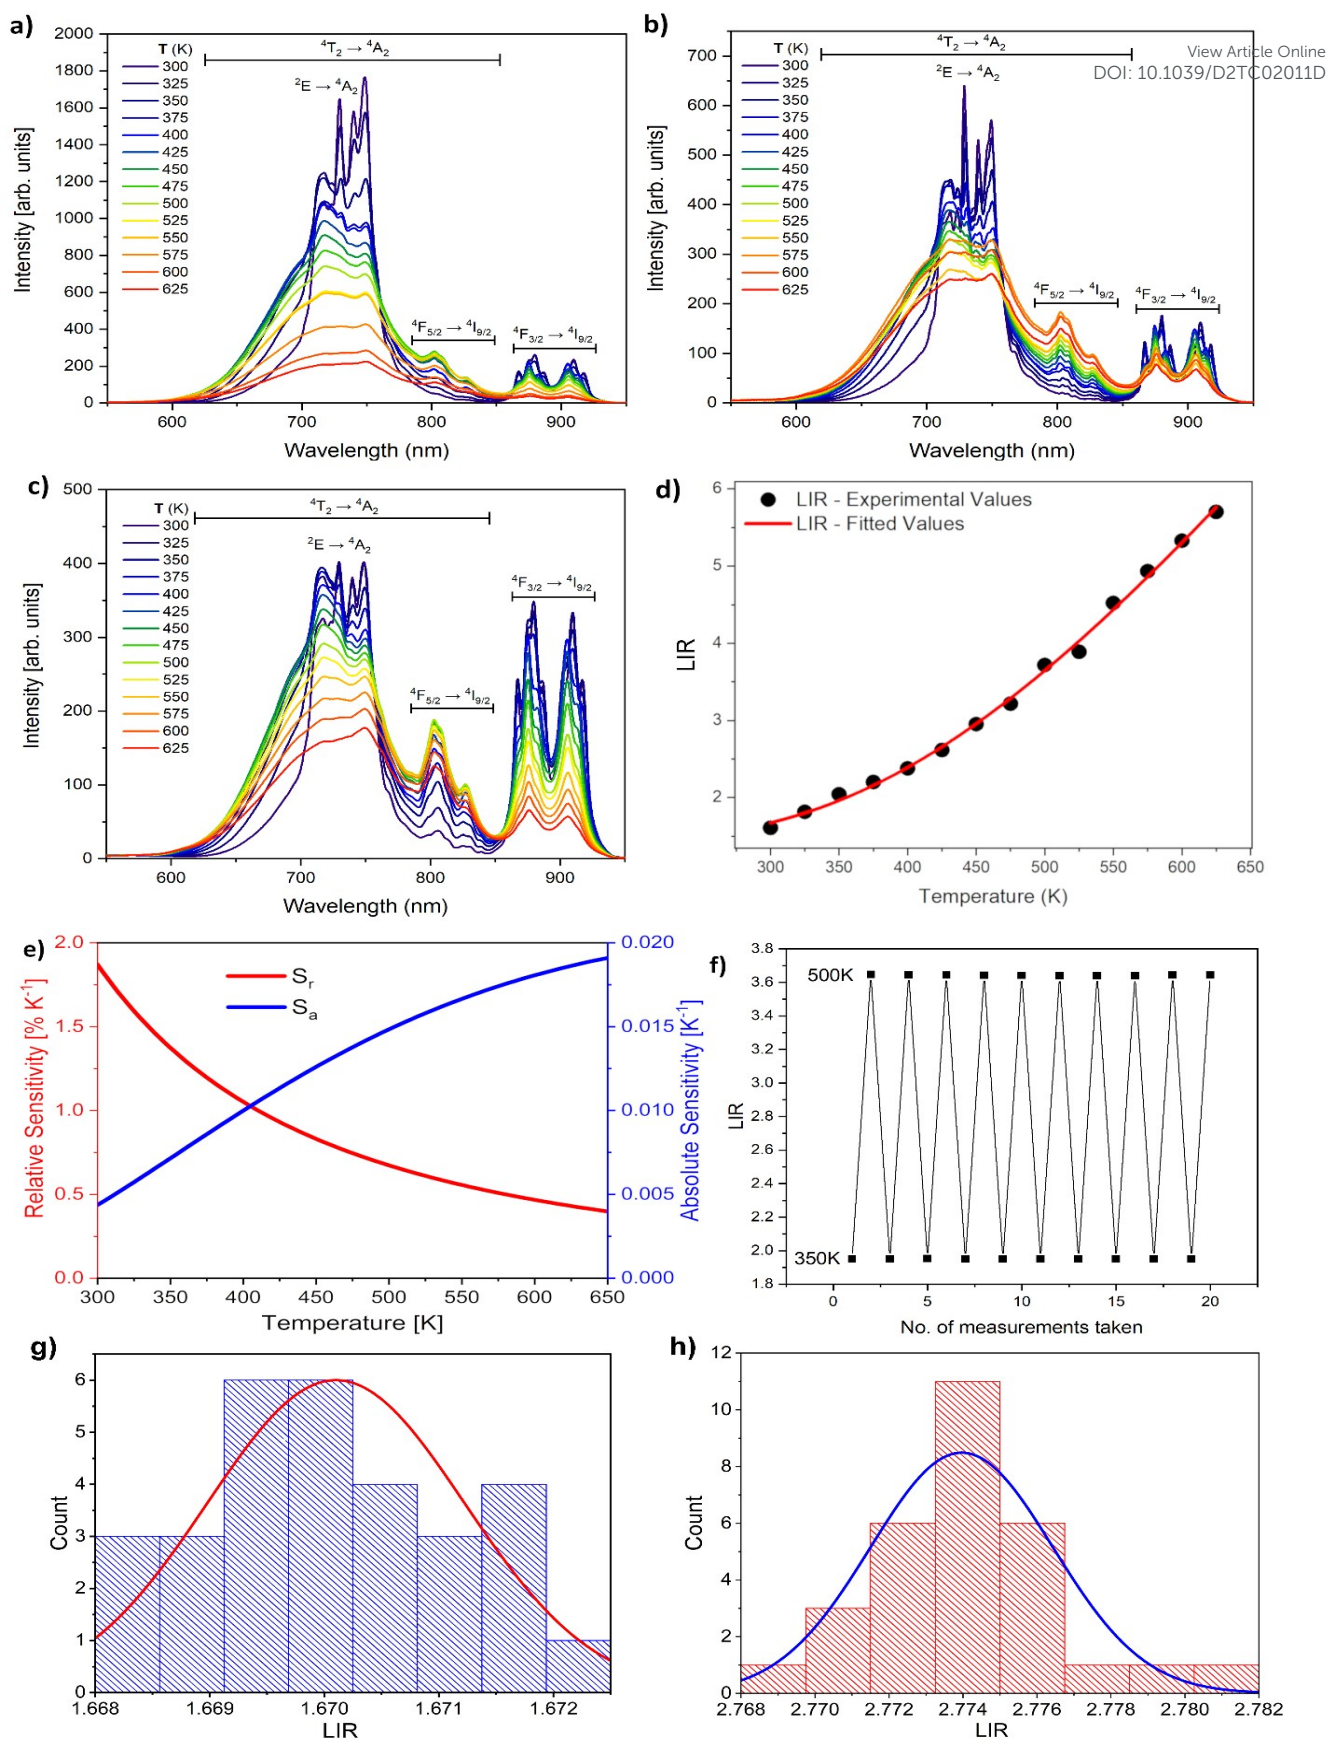


Figure 6: Emission spectra of a) Nd³⁺ x = 0.005 sample, b) x = 0.01, and c) Nd³⁺ x = 0.02 all excited at 473 nm. d) Fitted LIR of the x = 0.02 sample. e) Absolute (red) and relative (black) sensitivities of the x = 0.02 sample. f) Repeatability of the x = 0.02 sample's LIR by cycling between 350 and 500 K. Distribution curve of LIR after 30 consecutive measurements at g) 300 K, and h) 435 K.



ARTICLE

Table 2. Comparison of thermometric performance of Cr³⁺ or Nd³⁺ doped LGO, Cr³⁺,Nd³⁺ co-doped systems, or other prominent probes with LGO:Cr³⁺,Nd³⁺, by the LIR method.

Host	Activator	T range [K]	S _r [% K ⁻¹] @ 310 K	Max(S _r) [% K ⁻¹] @ 1]	S _a [K ⁻¹] @ 310 K	ΔT [K] @ 310 K	Min(ΔT) [K]	Ref.
ZnS	Mn ²⁺ ,Eu ³⁺	303-423	NA	1.1 @ 303 K	NA	NA	0.02	49
YF ₃	Er ³⁺ ,Yb ³⁺	293-473	1.8	2 @ 293 K	4.2 x 10 ⁻³	1.1	1	50
ZnSe/CdSe	Mn ²⁺	200-370	1.2	1.2 @ 310 K	NA	NA	NA	51
MgAl ₂ O ₄	Cr ³⁺	300-540	3.4	3.5 @ 300 K	4.0 x 10 ⁻³	0.3	0.3	52
ZnGa ₂ O ₄	Cr ³⁺	300-700	2.8	3.2 @ 300 K	1.4 x 10 ⁻³	0.4	0.4	53
Bi ₂ Ga ₄ O ₉	Cr ³⁺	150-450	0.7	0.75 @ 300 K	NA	1.5	1.5	54
Sr ₂ MgAl ₂₂ O ₃₆	Cr ³⁺	298-523	1.7	2 @ 300 K	4.5 x 10 ⁻¹	NA	NA	55
YVO ₄	Eu ³⁺	300-850	3.9	4.2 @ 300 K	5.8 x 10 ⁻⁷	NA	NA	56
La ₂ O ₃	Yb ³⁺ ,Nd ³⁺	290-1230	2.9	3 @ 300 K	1.4 x 10 ⁻⁴	0.7	0.6	57
Al ₂ O ₃	Sm ²⁺	298-648	4.7	4.8 @ 298 K	3.3 x 10 ⁻³	0.04	0.04	58
YAB	Pr ³⁺ ,Gd ³⁺	30-800	0.8	10 @ 30 K	NA	0.6	0.6	59
LiLuF ₄	Er ³⁺ ,Yb ³⁺	300-525	1.2	1.3 @ 300 K	NA	0.09	0.08	60
NaYF ₄	Er ³⁺ ,Yb ³⁺	300-900	1.1	1.1 @ 300 K	3.6 x 10 ⁻³	1	1	61
Ga ₂ S ₃ :La ₂ O ₃	Er ³⁺ ,Yb ³⁺	293-493	1.0	1.1 @ 293 K	NA	0.3	0.3	62
LGO	Cr ³⁺	150-300	0.7	2.07 @ 150 K	1.9 x 10 ⁻²	0.7	0.2	11
LGO	Nd ³⁺	280-830	1.5	1.8 @ 280 K	NA	1.2	1.6	12
LGO	V ⁿ⁺ ,Nd ³⁺	123-573	1.0	1.5 @ 350 K	NA	NA	NA	13
LGO	Cr ³⁺	300-600	2.4	2.5 @ 300 K	NA	0.05	0.05	15
Gd ₃ Al ₅ GaO ₁₂	Cr ³⁺ ,Nd ³⁺	123-573	1.2	1.9 @ 123 K	NA	NA	NA	24
LaScO ₃	Cr ³⁺ ,Nd ³⁺	123-573	0.2	1.3 @ 400 K	NA	NA	NA	25
LiLaP ₄ O ₁₂	Cr ³⁺ ,Nd ³⁺	113-473	3.6	3.9 @ 323 K	NA	NA	NA	31
LiLaP ₄ O ₁₂	Cr ³⁺ ,Nd ³⁺	300-420	NA	4.9 @ 323 K	NA	NA	0.05	32
YAG	Cr ³⁺ ,Nd ³⁺	100-850	3.3	3.5 @ 200 K	NA	NA	NA	47
YAGG	Cr ³⁺ ,Nd ³⁺	123-573	1.1	2.16 @ 220 K	NA	NA	NA	48
LGO	Cr ³⁺ ,Nd ³⁺	300-625	1.8	1.9 @ 300 K	4.9 x 10 ⁻³	0.04	0.04	This work

Conclusions

Phosphors of composition La_{1-x}Ga_{0.99}O₃: Cr_{0.01}, Nd_x (x = 0.005, 0.01, 0.02) were successfully synthesised by the solid-state method and structurally characterised by PXRD using Rietveld refinement. The excitation into the spin-allowed absorption bands of Cr³⁺ at 590 nm gives rise to both the narrow-band, spin-forbidden ²E emission of Cr³⁺ at 729 nm and the ⁴F_{3/2} → ⁴I_{9/2} line-like emissions of Nd³⁺ at around 890 nm. At room temperature, energy transfer both from Cr³⁺ → Nd³⁺ and from Nd³⁺ → Cr³⁺ was evident by examination of excitation spectra registered at the well-separated Nd³⁺ and Cr³⁺ emission wavelengths.

It is demonstrated that La_{0.98}Ga_{0.99}O₃: Cr_{0.01}, Nd_{0.02} can be used as an efficient NIR thermometer. This binary probe follows the Boltzmann relation, with good sensitivity values. Due to the

high intensities of both the Nd³⁺ and Cr³⁺ emissions, the absolute sensitivity has high values (S_r ~2.0% K⁻¹ at 300 K) and the uncertainties in measurement are low, leading to an excellent temperature resolution (0.04 K at 300 K), even for inexpensive non-state-of-the-art equipment. Demonstrating this low uncertainty, and therefore high temperature resolution, whilst employing instrumentation that is closer to that utilised in industry, gives this probe the unique advantage of authenticity in testing for potential real-world applications. The sensor also shows potential to be used for temperature measurements of biological samples *in vivo*, as both the excitation and emission can be reached within the first biological window.

Conflicts of interest

There are no conflicts to declare.



Acknowledgements

The authors acknowledge funding by NATO grant SPS.MYP G5751 (The Optical Nose Grid for Large Indoor Area Explosives Vapours Monitoring) and from the Ministry of Education, Science and Technological Development of the Republic of Serbia. ALM thanks EPSRC for a PhD studentship from the Doctoral Training Programme. We thank Peter Rodger and Gary Oswald for preliminary exploratory synthesis and PXRD data collection during the covid-19 pandemic.

Notes and references

- C. D. S. Brites, A. Millan and L. D. Carlos, *Lanthanides in luminescent thermometry Handbook on the Physics and Chemistry of Rare Earths*, 2016.
- C. D. S. Brites, P. P. Lima, N. J. O. Silva, A. Millán, V. S. Amaral, F. Palacio and L. D. Carlos, *Nanoscale*, 2012, **4**, 4799–4829.
- M. D. Dramićanin, *J. Appl. Phys.*, 2020, **128**, 040902.
- M. D. Dramićanin, *Methods Appl. Fluoresc.*, 2016, **4**, 042001.
- S. F. Collins, G. W. Baxter, S. A. Wade, T. Sun, K. T. V. Grattan, Z. Y. Zhang and A. W. Palmer, *J. Appl. Phys.*, 1998, **84**, 4649–4654.
- G. (Greg) Baxter, S. Wade, S. Collins, G. Monnom and E. Maurice, *Proceedings of SPIE - The International Society for Optical Engineering*.
- G. Blasse and B. C. Grabmaier, *Luminescent Materials*, Springer-Verlag, 1994.
- Ch. S. Kamal, T. K. V. Rao, T. Samuel, P. V. S. S. N. Reddy, J. B. Jasinski, Y. Ramakrishna, M. C. Rao and K. R. Rao, *RSC Adv.*, 2017, **7**, 44915–44922.
- T. Ishihara, H. Matsuda and Y. Takita, *J. Am. Chem. Soc.*, 1994, **116**, 3801–3803.
- L. Zhang, L. Dong, B. Shao, S. Zhao and H. You, *Dalton Trans.*, 2019, **48**, 11460–11468.
- A. Mondal and J. Manam, *Ceram. Int.*, 2020, **46**, 23972–23984.
- M. Back, J. Ueda, J. Xu, D. Murata, M. G. Brik and S. Tanabe, *ACS Appl. Mater. Interfaces*, 2019, **11**, 38937–38945.
- K. Kniec and L. Marciniak, *Phys. Chem. Chem. Phys.*, 2018, **20**, 21598–21606.
- Z. Li, X. Yu, T. Wang, S. Wang, L. Guo, Z. Cui, G. Yan, W. Feng, F. Zhao, J. Chen, X. Xu and J. Qiu, *J. Am. Ceram. Soc.*, DOI:10.1111/jace.18286.
- A. L. Mullins, A. Čirić, Z. Ristić, J. A. Gareth Williams, I. R. Evans, and M. D. Dramićanin, *J. Lumin.*, 2022, **246**, 118847.
- V. Lojpur, S. Čulubrk, M. Medić and M. Dramićanin, *J. Lumin.*, 2016, **170**, 467–471.
- S. Čulubrk, V. Lojpur, S. P. Ahrenkiel, J. M. Nedeljković and M. D. Dramićanin, *J. Lumin.*, 2016, **170**, 395–400.
- Lj. R. Đačanin, S. R. Lukić-Petrović, D. M. Petrović, M. G. Nikolić and M. D. Dramićanin, *J. Lumin.*, 2014, **151**, 82–87.
- S. Balabhadra, M. L. Debasu, C. D. S. Brites, L. A. O. Nunes, O. L. Malta, J. Rocha, M. Bettinelli and L. D. Carlos, *Nanoscale*, 2015, **7**, 17261–17267.
- V. K. Rai, D. K. Rai and S. B. Rai, *Sens. Actuators A Phys.*, 2006, **128**, 14–17.
- Y. Shen, X. Wang, H. He, Y. Lin and C.-W. Nan, *Compos Sci Technol*, 2012, **72**, 1008–1011.
- D. K. Amarasinghe and F. A. Rabuffetti, *Chem. Mater.*, 2019, **31**, 10197–10204.
- C. Matuszewska, K. Elzbieciak-Piecka and L. Marciniak, *J. Phys. Chem. C*, 2019, **123**, 18646–18653. DOI: 10.1039/D2TC02011D
- K. Elzbieciak, A. Bednarkiewicz and L. Marciniak, *Sens. Actuators B Chem.*, 2018, 96–102.
- K. Elzbieciak-Piecka, M. Suta and L. Marciniak, *Chem. Eng. J.*, 2021, **421**, 129757.
- A. Čirić, Z. Ristić, J. Periša, Ž. Antić and M. D. Dramićanin, *Ceram.*, 2021, **47**, 27151–27156.
- Z. Ristić, V. Đorđević, M. Medić, S. Kuzman, M. Sekulić, Ž. Antić and M. D. Dramićanin, *Meas. Sci. Technol.*, 2021, **32**, 054004.
- M. Back, E. Trave, J. Ueda and S. Tanabe, *Chem. Mater.*, 2016, **28**, 8347–8356.
- E. Glais, M. Pellerin, V. Castaing, D. Alloyeau, N. Touati, B. Viana and C. Chanéac, *RSC Adv.*, 2018, **8**, 41767–41774.
- A. N. Bashkatov, E. A. Genina, V. I. Kochubey and V. V. Tuchin, *J. Phys. D*, 2005, **38**, 2543–2555.
- L. Marciniak, A. Bednarkiewicz, D. Kowalska and W. Strek, *J. Mater. Chem. C*, 2016, **4**, 5559–5563.
- L. Marciniak, A. Bednarkiewicz and W. Strek, *Sens. Actuators B Chem*, 2017, **238**, 381–386.
- A. A. Coelho, J. Evans, I. Evans, A. Kern and S. Parsons, *Powder Diffr.*, 2011, **26**, S22–S25.
- H. M. Rietveld, *J. Appl. Crystallog.*, 1969, **2**, 65–71.
- A. Čirić, S. Stojadinović and M. D. Dramićanin, *Meas. Sci. Technol.*, 2019, **30**, 045001.
- M. Lerch, H. Boysen and T. Hansen, *J. Phys. Chem. Solids*, 2001, **62**, 445–455.
- A.M. Glazer, *Acta Crystallogr. Sect. B Struct. Crystallogr. Cryst. Chem.*, 1972, **28**, 3384–3392.
- R. D. Shannon, *Acta Cryst.*, 1976, 751–767.
- W. Mikenda and A. Preisinger, *J. Lumin.*, 1981, **26**, 53–66.
- H. Hua, J. Ueda, J. Xu, M. Back and S. Tanabe, *Inorg. Chem.*, 2021, acs.inorgchem.1c03074.
- W. Ryba-Romanowski, S. Golab, G. Dominiak-Dzik, I. Sokolska and M. Berkowski, .
- M. J. Weber and T. E. Varitimos, *J. Appl. Phys.*, 1971, **42**, 4996–5005.
- P. I. Paulose, G. Jose, V. Thomas, N. V. Unnikrishnan and M. K. R. Warriar, *J. Phys. Chem. Solids*, 2003, **64**, 841–846.
- J. Rocha, C. D. S. Brites and L. D. Carlos, *Chem. – Eur. J.*, 2016, **22**, 14782–14795.
- T. P. van Swieten, A. Meijerink and F. T. Rabouw, *ACS Photonics*, 2022, **9**, 1366–1374.
- A. Čirić, Z. Ristić, Ž. Antić and M. D. Dramićanin, *Phys. B Condens. Matter*, 2022, **624**, 413454.
- L. Marciniak, A. Bednarkiewicz, J. Drabik, K. Trejgis and W. Strek, *Phys. Chem. Chem. Phys.*, 2017, **19**, 7343–7351.
- K. Elzbieciak and L. Marciniak, *Front. Chem.*, 2018, **6**, 424.
- S. Wang, S. Westcott and W. Chen, *J. Phys. Chem. B*, 2002, **106**, 11203–11209.
- A. Čirić, J. Aleksić, T. Barudžija, Ž. Antić, V. Đorđević, M. Medić, J. Periša, I. Zeković, M. Mitrić and M. D. Dramićanin, *Nanomaterials*, 2020, **10**, 627.
- V. A. Vlaskin, N. Janssen, J. van Rijssel, R. Beaulac and D. R. Gamelin, *Nano Lett.*, 2010, **10**, 3670–3674.
- A. Čirić, Z. Ristić, J. Periša, Ž. Antić and M. D. Dramićanin, *Ceram. Int.*, 2021, **47**, 27151–27156.
- J. Ueda, M. Back, M. G. Brik, Y. Zhuang, M. Grinberg and S. Tanabe, *Opt. Mater.*, 2018, **85**, 510–516.




ARTICLE

Journal Name

- 54 M. Back, J. Ueda, M. G. Brik, T. Lesniewki, M. Grinberg, S. Tanabe, *Acs Appl. Mater. Inter*, 2018, **10**, 41512–41524
- 55 Q. Wang, Z. Liang, J. Luo, Y. Yang, Z. Mu, X. Zhang, H. Dong and F. Wu, *Ceram. Int.*, 2020, **46**, 5008–5014.
- 56 A. Ćirić, Ł. Marciniak and M. D. Dramićanin, *J. Appl. Phys.*, 2022, **131**, 114501.
- 57 G. Gao, D. Busko, S. Kauffmann-Weiss, A. Turshatov, I. A. Howard and B. S. Richards, *J. Mater. Chem. C*, 2018, **6**, 4163–4170.
- 58 A. Ćirić, S. Stojadinović, Z. Ristić, I. Zeković, S. Kuzman, Ž. Antić and M. D. Dramićanin, *Adv. Mater. Technol.*, 2021, **6**, 2001201.
- 59 D. Yu, H. Li, D. Zhang, Q. Zhang, A. Meijerink and M. Suta, *Light Sci. Appl.*, 2021, **10**, 236.
- 60 A. M. Kaczmarek, M. Suta, H. Rijckaert, T. P. van Swieten, I. V. Driessche, M. K. Kaczmarek and A. Meijerink, *J. Mater. Chem. C*, 2021, **9**, 3589–3600.
- 61 R. G. Geitenbeek, P. T. Prins, W. Albrecht, A. van Blaaderen, B. M. Weckhuysen and A. Meijerink, *J. Phys. Chem. C*, 2017, **121**, 3503–3510.
- 62 P. V. Dos Santos, M. T. De Araujo, A. S. Gouveia-Neto, J. A. M. Neto and A. S. B. Sombra, *IEEE J. Quantum Electron.*, 1999, **35**, 395–399.

View Article Online
DOI: 10.1039/D2TC02011D

Open Access Article. Published on 23 June 2022. Downloaded on 6/24/2022 3:58:18 PM.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Journal of Materials Chemistry C Accepted Manuscript